

Farzet Bikić, Dejana Kasapović

Faculty of Engineering and Natural Sciences, University of Zenica,  
Zenica, Bosnia and Herzegovina

Scientific paper

ISSN 0351-9465, E-ISSN 2466-2585

<https://doi.org/10.62638/ZasMat1165>



Zastita Materijala 66 ( )  
(2025)

## Investigation of general corrosion of austenitic stainless steel types 304 L and 317 L, especially from the aspect of their chemical composition

### ABSTRACT

*Austenitic stainless steels are among the most widely used types of stainless steel. The most commonly used grades are the American Iron and Steel Institute (AISI) 300 series of alloys. Starting from the basic 304 alloy (Fe-19Cr-10Ni), molybdenum is added to improve resistance to pitting (2-3 wt.% in the case of type 316 and 3-4 wt.% in type 317). Sensitisation due to chrome depletion during welding and other heat treatments, and the possible resultant intergranular corrosion, can be avoided through the use of low-carbon grades (304L, 316L, 317L, in which carbon is limited to 0.03 wt.% max.) or by adding titanium (type 321) or niobium and tantalum (type 347) to precipitate carbon at higher temperatures. The addition of chrome also imparts greater oxidation resistance, whilst nickel improves the ductility and workability of the material at room temperature.*

*In this paper, general corrosion of austenitic stainless steels, specifically low-carbon types 317 L and 304 L, was investigated. The research results are presented in the form of Tafel polarization curves, expressed through corrosion current density and open circuit potential. The results prove that the rate of general corrosion of the tested austenitic stainless steels decreases by lowering the temperature of the HCl solution, decreasing the concentration of HCl, and the presence of molybdenum in the composition of steel type 317 L.*

**Keywords:** austenitic stainless steels, general corrosion, 317 L, 304 L, Tafel polarization curves

### 1. INTRODUCTION

Stainless steels usually excellent resistance to corrosion is down to an ultrathin layer of oxides of especially chromium and iron, and although this film is only a few nanometres thick, it is still so dense and strong that the steel is effectively 'isolated' from the surrounding environment - similarly to an ultrathin paint. If, despite all precautions, a hole occurs in the protective oxide layer, it quickly restores itself, and the steel is again protected. This mechanism is called repassivation [1]. Austenitic stainless steels are among the most widely used types of stainless steel. The most commonly used grades are the American Iron and Steel Institute (AISI) 300 series of alloys. Starting from the basic 304 alloy (Fe-19Cr-10Ni), molybdenum is

added to improve resistance to pitting (2-3 wt.% in the case of type 316 and 3-4 wt.% in type 317). Sensitisation due to chrome depletion during welding and other heat treatments, and the possible resultant intergranular corrosion, can be avoided through the use of low-carbon grades (304L, 316L, 317L, in which carbon is limited to 0.03 wt.% max.) or by adding titanium (type 321) or niobium and tantalum (type 347) to precipitate carbon at higher temperatures. The addition of chrome also imparts greater oxidation resistance, whilst nickel improves the ductility and workability of the material at room temperature [2, 3].

In this paper, general corrosion of austenitic stainless steels, specifically low-carbon types 317 L and 304 L, will be investigated. The high corrosion resistance of stainless steel is attributed to the formation of a protective passive film on its surface. Many scholars have studied the characteristics of passive film. By direct imaging of native passive film on 304 stainless steel, Hamada demonstrated the enrichment of chromium in the film and the enrichment of nickel in the matrix side closest to

\*Corresponding author: Farzet Bikić

E-mail: farzet.bikic@unze.ba

Paper received: 30. 09. 2024.

Paper accepted: 10. 11. 2024.

the passive film/matrix interface [4]. Stainless steel has important characteristics such as versatility, durability, attractiveness and high mechanical and corrosion resistance [5]. General corrosion is also called acid corrosion as it is a type of corrosion that in stainless steel is often found in very acidic, but also in very alkaline media. As opposed to the four other types of stainless steel corrosion, general corrosion is characterised by both anode and cathode reactions taking place all over the surface. This means that the whole surface is activated and thereby corrodes more or less uniformly [1]. In non-passivating metals and alloys, general corrosion is the most common type of corrosion, but for passivable alloys it is relatively rare. Even in strong acids, stainless steel can achieve a certain level of passivity, and in practice there is a big difference between an acid that simply thins the

passive layer, but does not entirely dissolve it, and an acid that eats away the whole of the passive layer and immediately attacks the underlying steel. Relatively weak and pure acids (e.g. citric acid, acetic acid or formic acid) only thin the naturally occurring oxide layer slightly. The oxide layer is restored with the same speed, and corrosion loss is minimal - at least when the acids are pure. If the acids contain aggressive ions (especially chloride), the situation may become far worse, especially at high temperatures [1].

## 2. EXPERIMENTAL PART

AISI/ASTM 304 L and 317L steels were used for general corrosion testing of austenitic stainless steels. The chemical compositions of the mentioned steels are given in table 1.

Table 1. Chemical composition of tested austenitic stainless steels

AISI/ ASTM	Mas. %								
	C	Si	Mn	P <sub>max</sub>	S	N	Cr	Mo	Ni
317L	≤ 0,03	≤ 1,00	≤ 2,00	0,045	≤ 0,015	≤ 0,11	17,5-19,5	3-4	13-16
304L	≤ 0,03	≤ 1,00	≤ 2,00	0,045	≤ 0,015	≤ 0,11	18 -20	-	10-12

The test of general corrosion of austenitic stainless steels was carried at temperatures of 20 ±1 °C, 30 ±1 °C and 40 ±1 °C, in 0.5% HCl and 1% HCl solutions. The Tafel extrapolation method was used to examine general corrosion of 317 L and 304 L austenitic stainless steels. The Tafel extrapolation method involves scanning the potential of the working electrode of ±250 mV in relation to its open circuit potential  $E_{(I=0)}$ , at a speed of 0.5 mVs<sup>-1</sup>. Investigation of corrosion was conducted in a corrosion cell according to the Standard ASTM G5-94 [6], on a potentiostat/galvanostat instrument Princeton Applied Research, model 263A-2, with

PowerCORR® software, which is part of the Power Suite software package.

## 3. RESULTS AND DISCUSSION

The results of testing the general corrosion rate of selected austenitic stainless steels, using the Tafel extrapolation method, are shown in tables 2 and 3, but also in figures 1-8.

Table 2 but also Figures 1 and 2 show the influence of the concentration of HCl solution on the rate of general corrosion of austenitic stainless steel types 304 L 317 L.

Table 2. Corrosion rate of tested austenitic stainless steels in 0.5% and 1% HCl

AISI/ ASTM	t = 30 ±1 °C, 0,5 % HCl		t = 30 ±1 °C, 1 % HCl	
	$E_{(I=0)}$ , mV	$i_{cor}$ , $\mu\text{A cm}^{-2}$ (mmpy)	$E_{(I=0)}$ , mV	$i_{cor}$ , $\mu\text{A cm}^{-2}$ (mmpy)
304L	10,823	7,79(9,06·10 <sup>-2</sup> )	-334,42	6,71·10 <sup>1</sup> (7,79·10 <sup>-1</sup> )
317L	-22,314	5,907(6,86·10 <sup>-2</sup> )	-312,90	3,854·10 <sup>1</sup> (4,48·10 <sup>-1</sup> )

With an increase in the concentration of the HCl solution, there is an increase in the rate of general corrosion for both types of stainless steels, 304 L and 317 L. With an increase in the concentration of the HCl solution, there is an increase in the value of the corrosion current density  $i_{cor}$  for both types of stainless steels, Table 2 but also Figures 1 and 2. With an increase in the concentration of the HCl solution, the open circuit potential  $E_{(I=0)}$  shifts to more negative values for

both types of stainless steels, Table 2 but also Figures 1 and 2.

One of the most aggressive ions that cause general corrosion of stainless steels are chloride ions. Chlorides are able to remove the oxide of steel and then attack the steel itself. By adding chloride to an otherwise relatively harmless acid, you get diluted hydrochloric acid which will be far more corrosive to the steel than the pure, chloride-free acid [1].

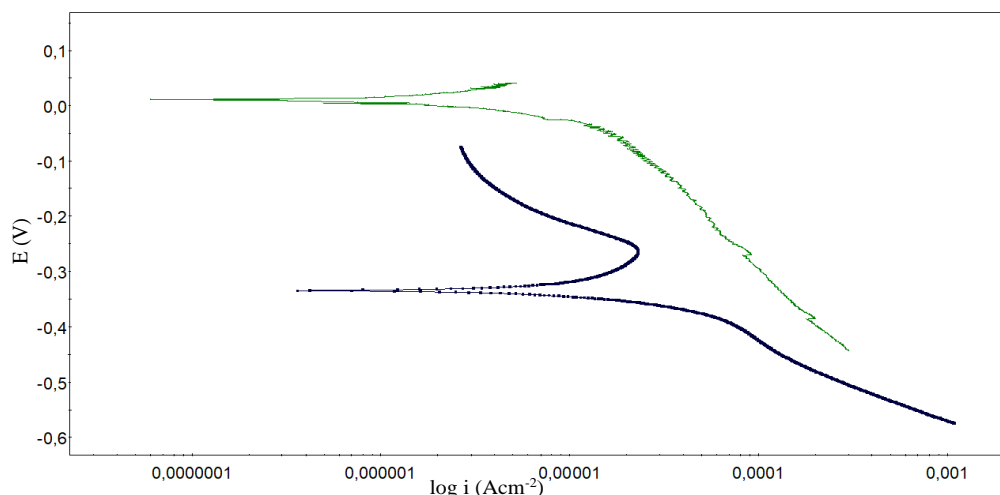


Figure 1. Tafel curves of samples ASTM 304 L ( $t=30\text{ }^{\circ}\text{C}$ , ---- 1% HCl, --- 0,5% HCl)

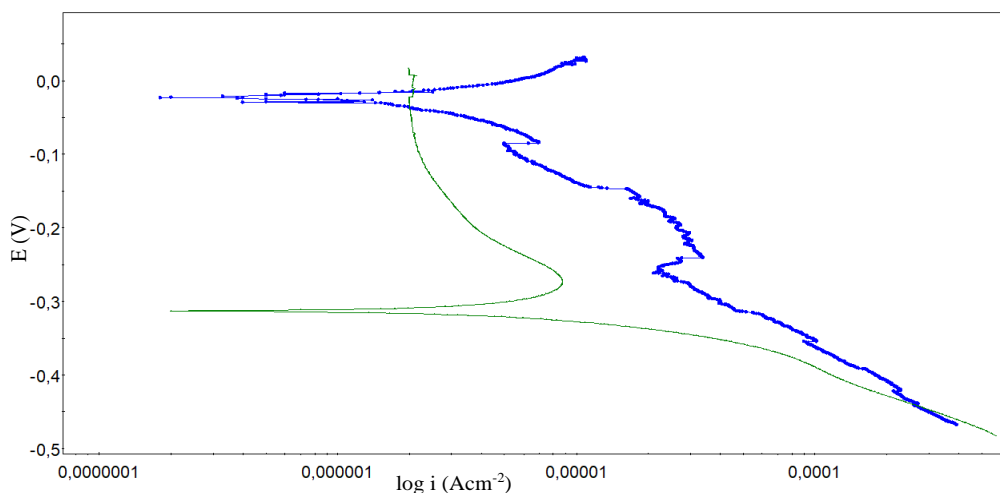


Figure 2. Tafel curves of samples ASTM 317 L ( $t=30\text{ }^{\circ}\text{C}$ , ---- 1% HCl, --- 0,5% HCl)

Table 3 but also Figures 3 and 4 show the influence of temperature on the rate of general corrosion of austenitic stainless steel types 304 L and 317 L.

Table 3. Corrosion rate of tested austenitic stainless steels in 0.5% HCl solution

AISI/ ASTM	$t = 20 \pm 1\text{ }^{\circ}\text{C}$		$t = 30 \pm 1\text{ }^{\circ}\text{C}$		$t = 40 \pm 1\text{ }^{\circ}\text{C}$	
	$E_{(I=0)}$ , mV	$i_{\text{cor}}$ , $\mu\text{Acm}^{-2}$ (mmpy)	$E_{(I=0)}$ , mV	$i_{\text{cor}}$ , $\mu\text{Acm}^{-2}$ (mmpy)	$E_{(I=0)}$ , mV	$i_{\text{cor}}$ , $\mu\text{Acm}^{-2}$ (mmpy)
304L	61,07	2,33( $2,71 \cdot 10^{-2}$ )	10,823	7,79( $9,06 \cdot 10^{-2}$ )	-146,71	35,4( $4,11 \cdot 10^{-1}$ )
317L	72,05	5,57( $6,47 \cdot 10^{-2}$ )	-22,314	5,91 ( $6,86 \cdot 10^{-2}$ )	-55,413	9,24 ( $1,07 \cdot 10^{-1}$ )

With increasing temperature of the HCl solution there is an increase in the rate of general corrosion for both types of stainless steels 304 L and 317 L. With increasing temperature of the HCl solution, there is an increase in the value of the corrosion current density  $i_{\text{cor}}$  for both types of stainless steels, Table 3 but also Figures 3 and 4. With increasing temperature of the HCl solution, the open circuit potential  $E_{(I=0)}$  shifts to more negative values for both types of stainless steels, Table 3 but also Figures 3 and 4. Temperature has an important effect on the corrosion of stainless steels. A rise in

temperature will generally lead to a decrease in the corrosion resistance [7]. Escrivà suggested that the passive films formed at high temperatures should be more defective [8]. This was beneficial for the mitigation of aggressive ions inside the passive film and consequently could accelerate the dissolution process and the exchange kinetics between the electrode surface and the electrolyte [9]. BenSalah found that higher temperatures tended to promote the formation of a porous film, thus leading to a decrease in the corrosion resistance [10].

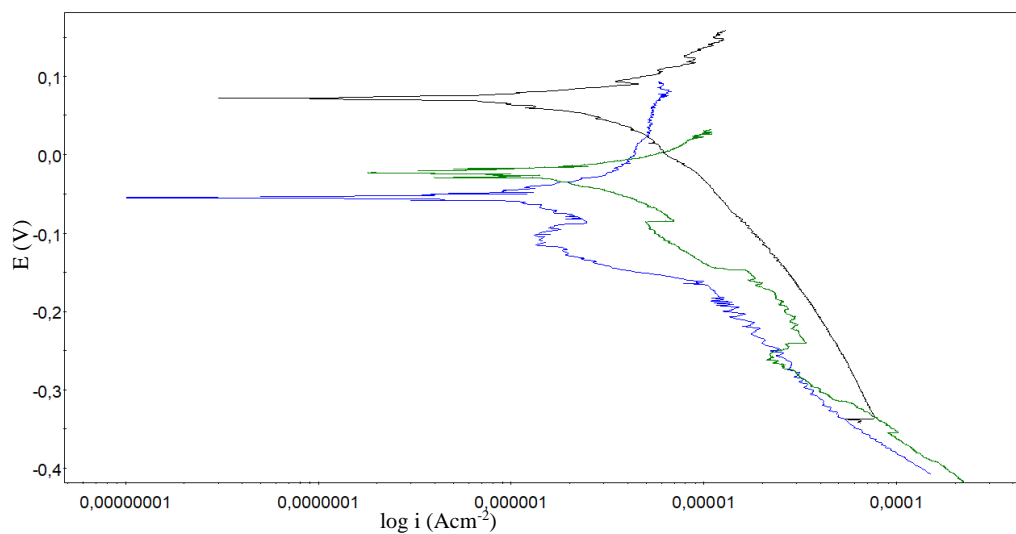


Figure 3. Tafel curves of samples ASTM 317 L tested in 0.5% HCl (---- 40 °C, ---- 30 °C, ---- 20 °C)

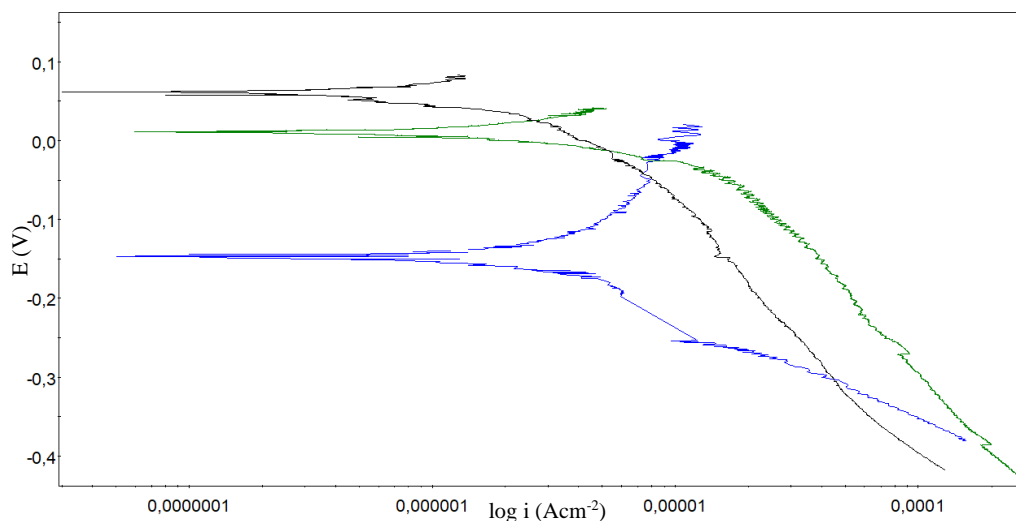


Figure 4. Tafel curves of samples ASTM 304 L tested in 0.5% HCl solution (---- 40 °C, ----30 °C, ---- 20 °C)

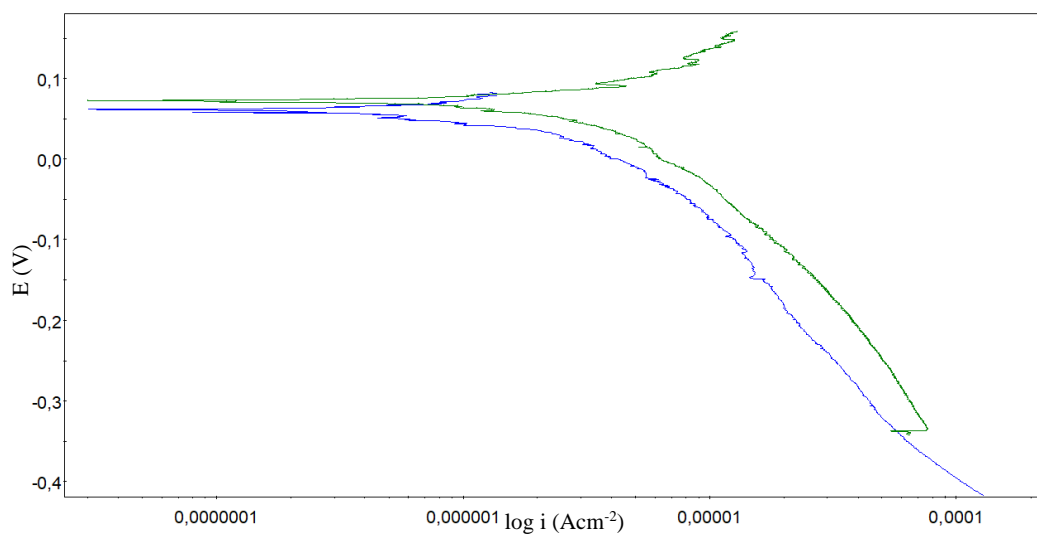


Figure 5. Tafel curves of samples tested in 0.5% HCl solution at 20 °C (--- 304 L, ---317 L)

Tables 2 and 3 but also Figures 5, 6, 7 and 8 show the influence of chemical composition on the rate of general corrosion of austenitic stainless steel types 304 L and 317 L.

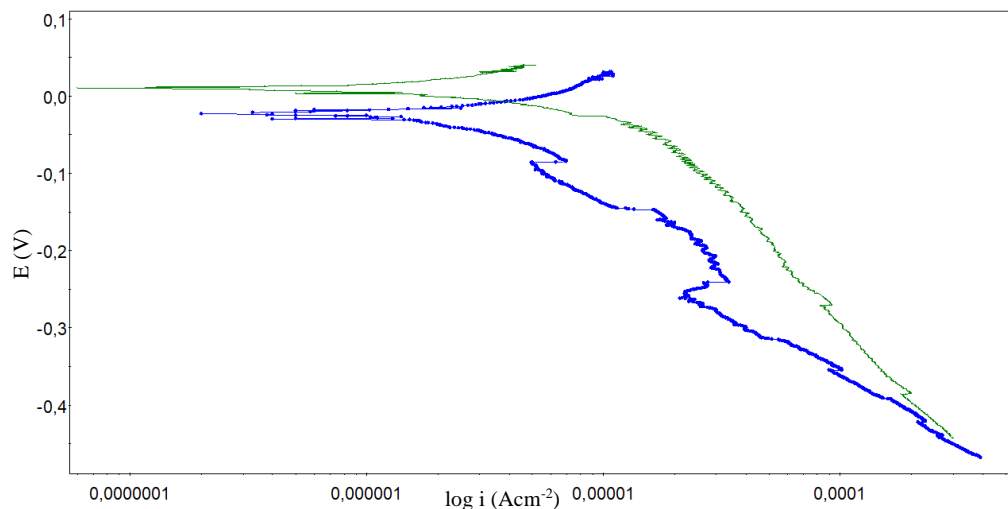


Figure 6. Tafel curves of samples tested in 0.5% HCl solution at 30 °C (--- 317 L, --- 304 L)

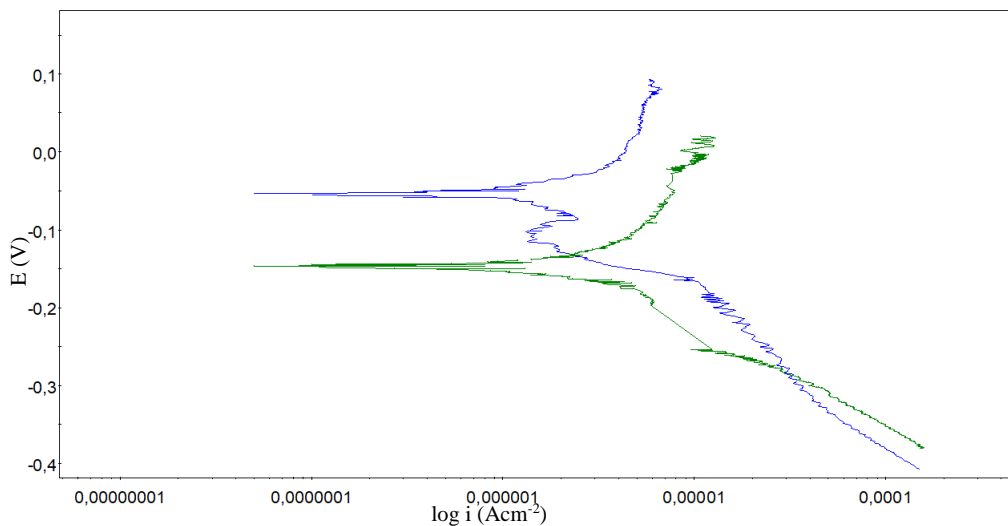


Figure 7. Tafel curves of samples tested in 0.5% HCl solution at 40 °C (--- 317 L, --- 304 L)

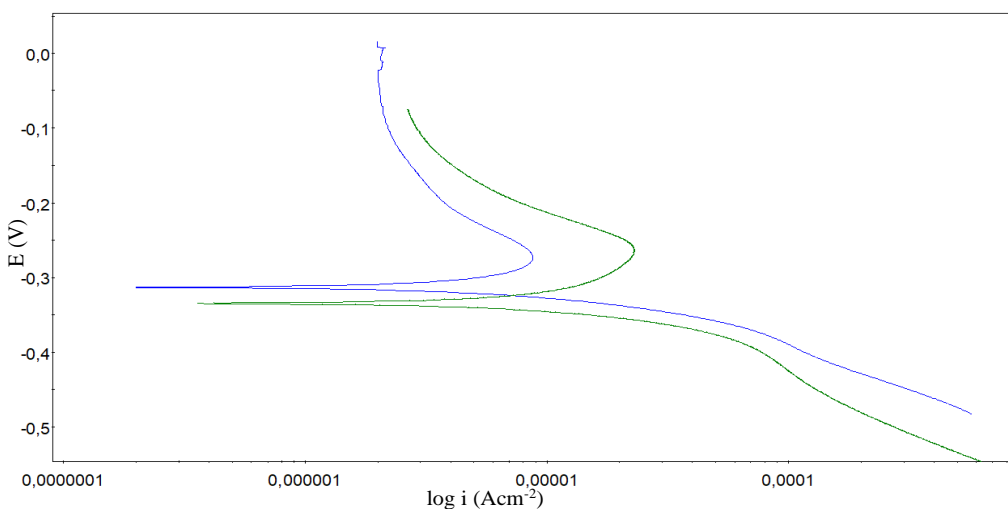


Figure 8. Tafel curves of samples tested in 1 % HCl at 30 °C (--- 317 L, --- 304 L)

The results shown in Tables 2 and 3 but also Figures 5, 6, 7 and 8 almost undoubtedly show a higher general corrosion resistance of stainless steel type 317 L compared to stainless steel type 304 L. Samples of stainless steel type 317 L at all tested temperatures, 20 °C, 30 °C and 40 °C, as well as in both tested HCl solutions, 0.5% HCl and 1% HCl, show lower values of corrosion current density  $i_{cor}$  and more positive values of open circuit potential  $E_{(I=0)}$  in relation to stainless steel samples of type 304 L. The only exception is the more positive value of the open circuit potential  $E_{(I=0)}$  of the stainless steel sample of type 304 L compared to the sample of stainless steel of type 317 L testing of general corrosion of the mentioned stainless steels at temperature 30 °C in 0.5% HCl solution, Table 3 and Figure 7.

The reason for the increase in corrosion resistance of 317 L stainless steel compared to 304 L stainless steel, looking at their chemical composition, should be the content of molybdenum in 317 L stainless steel, because the main difference between them is the absence of molybdenum in 304 L. Generally, the addition of molybdenum increases corrosion resistance of wrought austenitic stainless steels [11]. Addition Mo to austenitic stainless steels allows formation of a passive film consisted of a solid solution of  $Mo^{6+}$  in chromium oxyhydroxide network, which reduces the corrosion current density in the active region for acidic solution [12].

The beneficial effects of molybdenum have been interpreted as follows: molybdenum eliminates the active surface sites through the formation of molybdenum oxy-hydroxide or molybdate on these site, on which it is difficult to form the stable passive film. This leads to the appearance of a homogeneous steel surface and to the formation of a homogeneous passive film [13]. In the end, Pourbaix diagrams establish  $MoO_3$  as the only compound formed in strongly acidic media [14].

#### 4. CONCLUSION

Testing the influence of temperature of the HCl solution, HCl concentration and molybdenum content on the rate of general corrosion of austenitic stainless steels, it is concluded:

- With an increase in the concentration of the HCl solution, there is an increase in the rate of general corrosion for both types of stainless steels, 304 L and 317 L.
- With increasing temperature of the HCl solution there is an increase in the rate of general corrosion for both types of stainless steels 304 L and 317 L.
- Higher general corrosion resistance of stainless steel type 317 L compared to stainless

steel type 304 L. The reason for the increase in corrosion resistance of 317 L stainless steel compared to 304 L stainless steel, looking at their chemical composition, should be the content of molybdenum in 317 L stainless steel, because the main difference between them is the absence of molybdenum in 304 L. Generally the conclusion can be that the addition of molybdenum increases corrosion resistance of austenitic stainless steels.

#### 5. REFERENCES

- [1] C. Q. Jessen (2011) *Stainless Steel and Corrosion*, Damstahl a/s, Denmark.
- [2] F. King (2009) *Corrosion Resistance of Austenitic and Duplex Stainless Steels in Environments Related to UK Geological Disposal*, Quintessa Limited, QRS-1384C-R1, Version 1.2, UK.
- [3] F. Bikić, D. Mujagić (2014) Investigation of possibility for reducing AISI 303 stainless steel pitting corrosion by microalloying with boron or zirconium, *Bulletin of the Chemists and Technologists of Bosnia and Herzegovina*, 42, 41-46.
- [4] E. Hamada, K. Yamada, M. Nagoshi, N. Makiishi, K. Sato, T. Ishii, K. Fukuda, S. Ishikawa, T. Ujio (2010) Direct imaging of native passive film on stainless steel by aberration corrected STEM, *Corros. Sci.*, 52, 3851-3854.
- [5] E. Kikuti, R. Conrado, N. Bocchi, S. R. Biaggio, R.C. Rocha-Filho (2004) Chemical and Electrochemical Coloration of Stainless Steel and Pitting Corrosion Resistance Studies, *J. Braz. Chem. Soc.*, 15 (4), 472-480.
- [6] ASTM G5 (1994) Standard Reference Test Method for Making Potentiostatic and Potentiodynamic Anodic Polarization Measurements.
- [7] Z. Wang, Z. Feng, L. Zhang (2020) Effect of high temperature on the corrosion behavior and passive film composition of 316 L stainless steel in high  $H_2S$ -containing environments, *Corrosion Science*, 174, 108844.
- [8] C. Escrivà-Cerdán, E. Blasco-Tamarit, D.M. García-García, J. García-Antón, A. Guenbour (2012) Passivation behaviour of Alloy 31 (UNS N08031) in polluted phosphoric acid at different temperatures, *Corros. Sci.*, 56, 114-122.
- [9] H. Iken, R. Basseguy, A. Guenbour, A.B. Bachir (2007) Classic and local analysis of corrosion behaviour of graphite and stainless steels in polluted phosphoric acid, *Electrochim. Acta*, 52, 2580-2587.
- [10] M. BenSalah, R. Sabot, E. Triki, L. Dhoubi, P. Refait, M. Jeannin (2014) Passivity of Sanicro28 (UNS N-08028) stainless steel in polluted phosphoric acid at different temperatures studied by electrochemical impedance spectroscopy and Mott-Schottky analysis, *Corros. Sci.*, 86, 61-70.
- [11] A. Szewczyk-Nykiel (2015) The influence of molybdenum on corrosion resistance of sintered austenitic stainless steels, *Technical Transactions Mechanics*, 4-M (26), p. 131 - 142.
- [12] K. Sugimoto, Y. Sawada (1977) The role of molybdenum additions to austenitic stainless steels

- in the inhibition of pitting in acid chloride solutions, Corrosion Science, 17 (5), 425-445
- [13] K. Hashimoto, K. Asami, K. Teramoto (1979) An X-ray photo-electron spectroscopic study on the role of molybdenum in increasing the corrosion resistance of ferritic stainless steels in HCl, Corrosion Science, 19(1), 3-14
- [14] A. Pardo, M.C. Merino, A.E. Coy, F. Viejo, R. Arrabal, E. Matykina (2008) Effect of Mo and Mn additions on the corrosion behaviour of AISI 304 and 316 stainless steels in H<sub>2</sub>SO<sub>4</sub>, Corrosion Science Volume 50, Issue 3, March, p. 780-794.

## IZVOD

### ISPITIVANJE OPĆE KOROZIJE AUSTENITNIH NEHRĐAJUĆIH ČELIKA TIPOVA 304 L I 317 L, POSEBNO S ASPEKTA NJIHOVOG HEMIJSKOG SASTAVA

Austenitni nehrđajući čelici su među najčešće korištenim vrstama nehrđajućih čelika. tipova 317 L i 304 L. Rezultati istraživanja prikazani su u obliku Tafelovih polarizacijskih Najčešće korištene kvalitete su legure serije 300 Američkog instituta za željezo i čelik (AISI). Polazeći od osnovne legure 304 (Fe-19Cr-10Ni), molibden 317). Senzibilizacija se dodaje za poboljšanje otpornosti na piting (2-3 mas.% u slučaju tipa 316 i 3-4 mas.% u tipu zbog smanjenja sadržaja hroma tokom zavarivanja i drugih toplinskih obrada, te moguća posljedična interkristalna korozija, može se izbjeći korištenjem niskougljičnih razreda (304L, 316L, 317L, u kojima je ugljik ograničen na 0,03 mas.% max.) ili dodavanjem titanijuma (tip 321) ili niobijuma i tantala (tip 347) za taloženje ugljika na višim temperaturama. Dodatak hroma također daje veću otpornost na oksidaciju, dok nikl poboljšava duktilnost i obradivost materijala na sobnoj temperaturi.

U ovom radu istraživana je opšta korozija austenitnih nehrđajućih čelika, posebno niskougljičnih krivulja, izraženi kroz struju korozije i potencijal otvorenog kruga. Rezultati pokazuju da se brzina opće korozije ispitivanih austenitnih nehrđajućih čelika smanjuje snižavanjem temperature, smanjenjem koncentracije otopine HCl, te prisustvom molibdena u sastavu čelika tipa 317 L.

**Ključneriječi:** austenitni nehrđajući čelik, opšta korozija, 317 L, 304 L, Tafelove polarizacijske krive

Naučni rad

Rad primljen: 30.09.2024.

Rad prihvaćen: 10.11.2024.

Farzet Bikić: <https://orcid.org/0009-0002-9797-8883>

Dejana Kasapović: <https://orcid.org/0009-0003-2066-6053>