

A. S. FOU DA¹, A. M. EL-DESOKY²,
A. A. KESHK³

Scientific paper
UDC:620.193.197

Inhibitive effect of azine and diazine derivatives on the corrosion of 316L SS in acidic media

The inhibiting effect of some azine and diazine derivatives on the corrosion of cyclic stressed 316L SS specimens in 3 M HCl in the presence of organic derivatives with concentrations (1×10^{-6} M – 11×10^{-6} M) at 30°C was studied using weight loss and galvanostatic polarization techniques. The inhibition of these derivatives on the uniform corrosion was evaluated by anodic and cathodic polarization curves of the electrode in the tested media. The examined derivatives exerted an inhibiting action towards corrosion. Polarization studies revealed that these derivatives behave as mixed inhibitors and inhibit corrosion by parallel adsorption on the specimen surface due to the presence of more than one active centre in the inhibitor molecule. The adsorption obeyed Temkin adsorption isotherm. The inhibitor efficiency increases with increasing the concentration of the inhibitor and decreases with increasing the value of the cyclic stress. Addition of I⁻, Br⁻ and SCN⁻ ions to the solution containing organic derivatives increases the inhibition efficiency of the system.

Keywords: Organic derivatives; Inhibition; Cyclic stress; Acidic media; 316L SS.

1. INTRODUCTION

Stress corrosion cracking (SCC) is one of the most serious corrosion problems facing metallic materials during their service life. Much attention has been paid to avoid or eliminate the damage of metallic materials due to SCC especially when there is a cyclic stress on the metallic material. SCC is sensitive to the composition of the corrosion environment; the addition of small amount of proper inhibitor mitigated SCC of austenitic steels in acidic media [1].

Benzotriazole (BTA) decreased the susceptibility of SCC for 18Cr-9Ni-Ti stainless steel in acidic chloride solution [1]. Inhibitors such as phenylthiourea, benzotriazole and acridine significant influence in the case of SCC tests with constant load than in constant strain rate testing (CSRT) [2]. Other inhibitors such as benzimidazole-2-thiol, benzothiazole-2-thiol, phenylthiourea and a mixture of n-decylamine + KI were found to be effective in the case of SCC tests by slow strain rate (SSRT) and U-bend [3,4].

The synergistic inhibition effect of iodine ions with some amines in NaCl solution on SCC of AISI

321 stainless steel was attributed to the effect of retarding both anodic and cathodic reactions of the corrosion processes [5]. SCC of AISI 321 stainless steel in acidic solution was inhibited by thiourea and its derivatives, primary amines and tetra-amine salts and estimating the anodic and cathodic action coefficients of the corrosion process, it was found that those inhibitors reduced the rate of anodic dissolution of the steel [6,7].

The previous studies were mostly performed by SSRT combined with observation of the morphology of fractured specimens and electrochemical measurements of unstressed specimens. It is expected that in situ electrochemical measurements of the corrosion rate of stressed specimens under dynamic straining condition may offer some interesting information on the role of an inhibitor.

In this paper, the inhibition effect of organic derivatives on the corrosion fatigue (CF) of 316L SS specimens stressed by cyclic stress with cyclic frequency of 10.5 Hz while immersed in hydrochloric acid solution is assessed by using in situ measurements of electrochemical galvanostatic polarization.

2. EXPERIMENTAL DETAIL

2.1. Materials and solution

The chemical composition and mechanical properties of specimen material are given in Tables 1 and 2).

Author's address: ¹Department of Chemistry, Faculty of Science, El-Mansoura University, El-Mansoura-35516, Egypt, ²Chemistry Department, High Institute of Engineering & Technology (New Damietta), Egypt, ³Department of Chemistry, Faculty of Science, University of Tabuk, Tabuk, Saudi Arabia

Received for Publication: 17. 07. 2014.

Accepted for Publication: 14. 09. 2014.

Table 1 - Chemical composition (wt %) of the 316L SS


Material Type	Percent composition								
	C	Mn	P	S	Si	Cr	Ni	Mo	Cu
316L SS	0.02	1.0	0.054	0.02	1.0	16	11	3	0.2

Table 2 - The mechanical properties of 316L SS


Yield stress (Mpa)	Tensile strength (Mpa)	Elongation (Lo=5do)%
335	322	19

HCl, KSCN, KI, KBr and organic permidine derivatives all of BDH made were used for preparing solutions. The names and molecular structures of the derivatives are given in bellow:


Series 1



pyrazine-2,3-dicarboxamide




3-aminopyrazine-2-carboxylic acid




pyrazin-2-amine

Series 2



pyridin-2-amine



pyridine-2,3-diamine

Series 1: (I) > (II) > (III)

Series 2: (IV) > (V)

2.2. Experimental

2.2.1. Chemical Technique (Weight loss method)

The reaction basin was graduated glass vessel 6 cm inner diameter and having a total volume of 250 ml. 100 ml of the test solution were employed in each experiment. The test pieces were cut into 2×2×0.2 cm. They were mechanically polished with emery paper (a coarse paper was used initially and then progressively finer grades were employed), rinsed with double distilled water and finally dried between two filter papers and weighed. The test pieces were suspended by suitable glass hooks at the edge of the basin, and under the surface of the test solution by about 1cm. After specified periods of time, 3 test pieces were taken out of the test

solution, rinsed with double distilled water, dried as before and weighed again. The average weight loss at a certain time for each set of three samples was taken. The weight loss was recorded to the nearest 0.0001g.

2.2.2-Electrochemical technique (Galvanostatic polarization method)

a. Electrodes

Chemical composition of 316L SS used in this study is given in Table 1. Two different types of electrodes were used; disks with 12 mm diameter and 2 mm thickness and cylindrical specimens. The discs were welded from one side to a copper wire for electric connection and embedded in glass tube of larger diameter than the sample. Epoxy

resin was used to stick the sample to the glass tube except the exposed tested surface area which was left to be exposed to the corrosive media.

Cylindrical specimens were used in the fatigue test and in electrochemical measurements after fatigue test in air. The specimen diameter was 10 mm while the gage length of the middle part was

20 mm and its diameter was 4 mm, and the overall length was 140 mm as shown in Figure 1. The gage length of all specimens were prepared by treatment with emery papers n. 1000, then degreased in acetone ultrasonic bath, washed with bi-distilled water and dried.

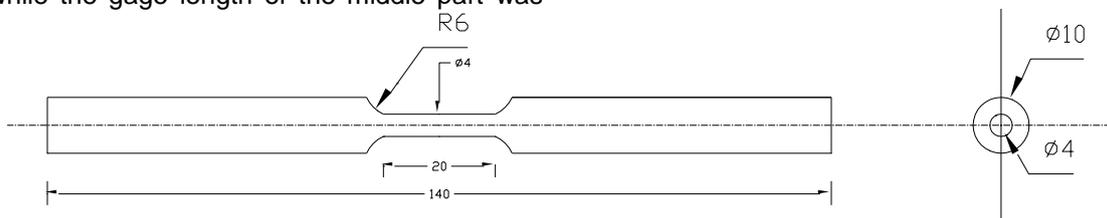


Figure 1 - Specimen of fatigue test (Dim. mm)

Fatigue tests were performed at 10.5 Hz on a cantilever rotary-bending fatigue test machine, with different cyclic stress (82MPa – 247MPa) and number of cycles (63000). The specimens were coated with epoxy resin except the test section that immersed in the solution during the entire galvanostatic polarization test. The corrosive media used was 3 M HCl. Solutions containing (1×10^{-6} M – 11×10^{-6} M) organic derivatives were used as inhibitors.

3. EXPERIMENTAL RESULTS AND DISCUSSION

3.1-Weight loss measurements

3.1.1-Effect of inhibitors concentrations

Weight-loss of 316L SS was determined, using equation (1), at various time intervals in absence and presence of different concentrations of organic derivatives, derivatives (I-V). The obtained weight loss-time curves are represented in Figure 2 for inhibitor (I), the most effective one. Similar curves were obtained for other inhibitors (not shown).

$$\Delta w = (w_1 - w_2) / A \quad (1)$$

Where Δw is the weight loss in mg per unit area, w_1 and w_2 are the weights of the specimen before and after reaction, respectively, and A is the surface area in cm^2 .

The curves obtained in the presence of inhibitors fall significantly below that of free acid. In all cases, the increase in the inhibitor concentration was accompanied by a decrease in weight-loss and an increase in the percentage inhibition. These results lead to the conclusion that, these derivatives under investigation are fairly efficient as inhibitors for 316L SS dissolution in hydrochloric acid solution. Also, the degree of surface coverage (θ) by the inhibitor, calculated from equation (2), would increase by increasing the inhibitor concentration.

$$\theta = 1 - (\Delta W_{inh.} / \Delta W_{free}) \quad (2)$$

Where ΔW_{inh} and ΔW_{free} are the weight losses per unit area in presence and absence of the inhibitor respectively.

In order to get a comparative view, the variation of the inhibition efficiencies (IE%) of the inhibitors with their molar concentrations were calculated according to equation (3); values obtained are summarized in Table 3.

$$\%IE = \theta \times 100 \quad (3)$$

Careful inspection of these results showed that, at the same inhibitor concentration, the order of inhibition efficiencies was as follow:

Series 1: (I) > (II) > (III)

Series 2: (IV) > (V)

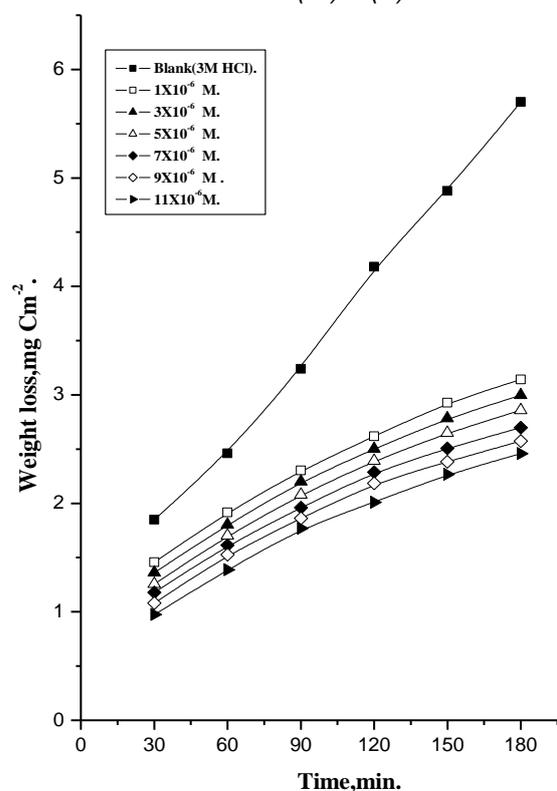


Figure 2 – Weight loss-time curves for the dissolution of 316 SS in absence and presence of different concentrations of compound (I) at 30°C

Table 3 - % Inhibition of 316L SS dissolution at 120 min. immersion in 3 M HCl in presence of different concentrations of inhibitors at 30°C.

Concentration, M	% Inhibition				
	(I)	(II)	(III)	(IV)	(V)
1×10^{-6}	68.4	61.3	56.7	44.3	37.1
3×10^{-6}	71.5	65.7	59.3	47.7	40.5
5×10^{-6}	74.1	68.1	63.6	50.0	42.3
7×10^{-6}	77.0	71.2	65.4	53.1	45.2
9×10^{-6}	78.3	74.1	67.2	55.3	47.1
11×10^{-6}	81.2	77.3	70.8	59.1	51.2

3.2. Synergistic effect

As seen from Table 3, the percentage inhibition efficiency of the tested derivatives is low, so in order to increase these values we use KI, KSCN, and KBr in addition to the different concentrations of the investigated derivatives. Table 4 shows the % In. of the investigated derivatives in presence of 1×10^{-2} M of KI.

Table 4 - % Inhibition efficiency of 316L SS dissolution at 120 min. immersion in 3M HCl in presence of 1×10^{-2} M KI at different concentrations of inhibitors at 30°C.

Concentration, M	% Inhibition				
	(I)	(II)	(III)	(IV)	(V)
1×10^{-6}	78.2	70.2	65.0	57.2	54.2
3×10^{-6}	81.3	73.3	68.0	61.1	57.1
5×10^{-6}	83.7	76.2	71.2	64.3	59.1
7×10^{-6}	86.1	79.2	74.3	68.1	62.0
9×10^{-6}	89.0	82.1	78.5	72.0	65.1
11×10^{-6}	91.0	85.3	80.4	74.3	67.2

It can be seen from Table 4 that the addition 10^{-2} M of KI, and inhibits the corrosion of 316L SS to a large extent and by increasing the concentration of hydrazide derivatives (1×10^{-6} - 11×10^{-6} M) the percentage inhibition increases. This can be interpreted according to Schmitt and Bedbur [8], which proposed two types of joint adsorption namely competitive and cooperative. In competitive adsorption, the anions and cations are adsorbed at different sites on the electrode surface, and in case of cooperative adsorption, the anions are chemisorbed on the electrode surface and the cations are adsorbed on a layer of the anion, apart from the adsorption on the surface directly.

From the data of Table 4 it is seen that KI would be considered as one of the effective anions for synergistic action with respect to the investigated salts. The net increment of inhibition efficiency shows a synergistic effect of KI, KSCN and KBr with hydrazide derivatives. The synergistic effect

depends on the type and concentration of anions. The inhibition efficiency in presence of these anions decreases in the order: KI > KSCN > KBr [9]. The experimental results suggested that the presence of these anions in the solution stabilizes the adsorption of derivatives on the metal surface and improved the inhibition efficiency of these derivatives.

The figure 3 demonstrates the mass- loss time curves for the dissolution of 316L SS in 3 M HCl in absence and presence of different concentrations of compound (b) without and with addition of 10^{-2} M KI at 30°C.

$$S_{\theta} = (1 - \theta_{1+2}) / (1 - \theta'_{1+2}) \quad (3)$$

$$\text{where } \theta_{1+2} = \theta_1 + \theta_2 - \theta_1 \theta_2$$

θ'_{1+2} - measured surface coverage by the anion in combination with cation. θ_1 and θ_2 are the surface coverage for anions and cations, respectively.

Table 5 lists the variation of the synergistic parameter (S_{θ}) in the presence of different concentrations of derivatives. It is seen that all values of (S_{θ}) are less than unity and, therefore, the adsorption of each compound antagonizes the other's adsorption. Thus, derivatives significantly improved the coverage and thus the quality and inhibition efficiency of derivatives on the corroding 316L SS.

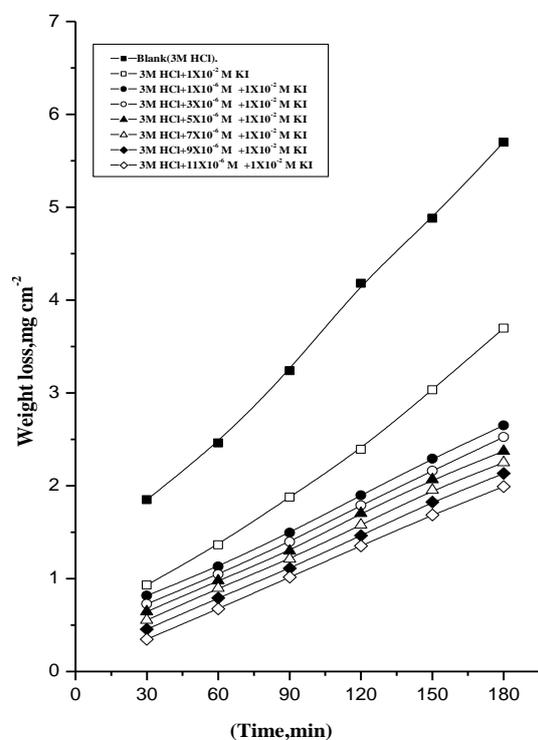


Figure 3 - Weight loss-time curves for 316 SS dissolution 3M HCl in absence and presence of 1×10^{-2} M KI and different concentrations of inhibitor (I) at 30°C

Derivatives are nitrogen organic derivatives, which contain unshared electron pairs. In strong acidic solutions these derivatives may be protonated, leading to positive charge in molecule. It is also known that 316L LSS surface has positive charge due to ($E_{corr}-E_q=0$), thus it is difficult for the positively charged derivatives to approach the positively charged 316LL SS surface, due to the electrostatic repulsion, this is why these derivatives can not act as excellent inhibitors for 316LL SS corrosion in 3M HCl solution without containing anions. In case of presence I^- , SCN^- and Br^- ions, these anions adsorbed on 316LL SS surface and makes the surface negatively charged by means of electrostatic attraction, after that, protonated hydrazide derivatives are easily reached the surface of 316LL SS.

Table 5 - Synergism parameter (S_θ) for different concentrations of inhibitors for 316L S dissolution in 3M HCl with addition of $1 \times 10^{-2} M$ KI at 30 °C.

Concentration	Synergism parameter (S_θ)				
	(I)	(II)	(III)	(IV)	(V)
1×10^{-6}	1.0	1.1	1.1	1.1	1.1
3×10^{-6}	1.0	1.1	1.0	1.1	1.1
5×10^{-6}	1.0	1.1	1.1	1.0	1.1
7×10^{-6}	1.0	1.1	1.1	1.1	1.1
9×10^{-6}	1.2	1.2	1.0	1.2	1.0
11×10^{-6}	1.4	1.2	1.1	1.2	1.1

3.3. Adsorption isotherm:

Assuming the corrosion inhibition was caused by the adsorption of hydrazide derivatives, and the values of surface coverage for different concentrations of inhibitors in 3M HCl were evaluated from mass loss measurement using the following equation:

$$\theta = [Weight\ loss_{(pure)} - Weight\ loss_{(inh.)}] / Weight\ loss_{(pure)} \tag{4}$$

From the values of (θ), it can be seen that the values of (θ) increased with increasing the concentration of derivatives. Using these values of surface coverage, one can utilize different adsorption isotherms to deal with experimental data. The Temkin adsorption isotherm was applied to investigate the adsorption mechanism, by plotting (θ) vs $\log C$, a straight lines were obtained Figure 4. On the other hand, it is found that Kinetic- thermodynamic model of El-Awady et al [9] which has the formula:

$$\log (\theta / 1 - \theta) = \log K' - y \log C \tag{5}$$

Is valid and verify the present adsorption data Figure 6. The equilibrium constant of adsorption K

= $K^{(1/y)}$, where 1/y is the number of the surface active sites occupied by one hydrazide molecule and C is the bulk concentration of the inhibitor. From Table 6 it is noted that ΔG_{ads} values have a negative sign indicating that the adsorption process proceeds spontaneously and increase as the percentage inhibition increases. Table 6 shows the calculated thermodynamic parameters.

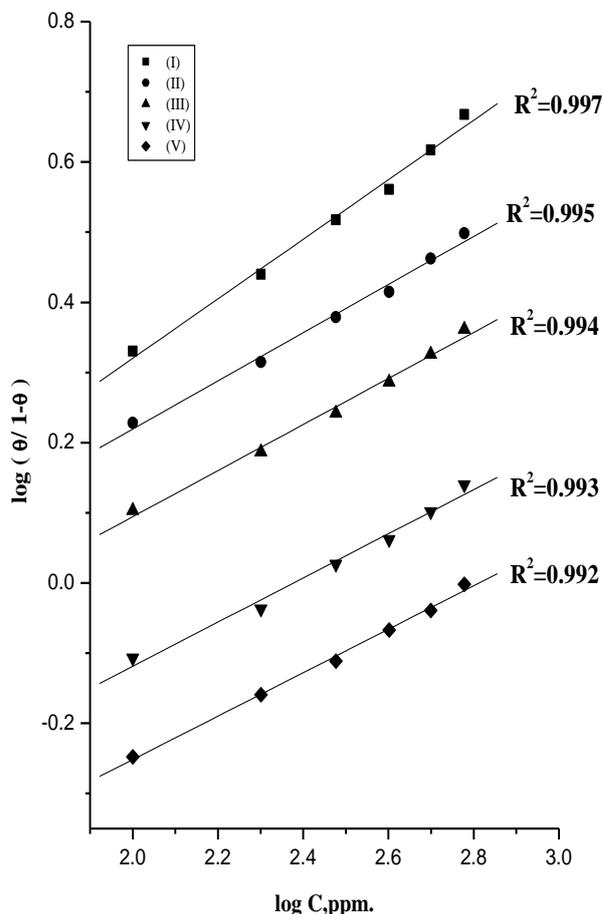


Figure 4 - Curve fitting of corrosion data for 316L SS in 3M HCl in presence of different concentrations of inhibitors (I) to the kinetic model at 30 °C

Table 6 - Inhibitor binding constant (K), free energy of binding (ΔG_{ads}), number of active sites (1/y) and later interaction parameter (a) for inhibitors derivatives at 30°C.

Inhibitors	Kinetic model			Temkin		
	1/y	K	$-\Delta G_{ads}$, kJmol ⁻¹	a	K	$-\Delta G_{ads}$, kJmol ⁻¹
(I)	3.200	0.985	60.7	14.03	72.3	63.0
(II)	3.121	0.874	58.9	13.33	67.1	62.2
(III)	3.023	0.655	54.5	13.24	17.1	52.1
(IV)	2.897	0.572	52.4	12.99	2.53	37.5
(V)	2.313	0.435	48.27	12.82	1.16	31.6

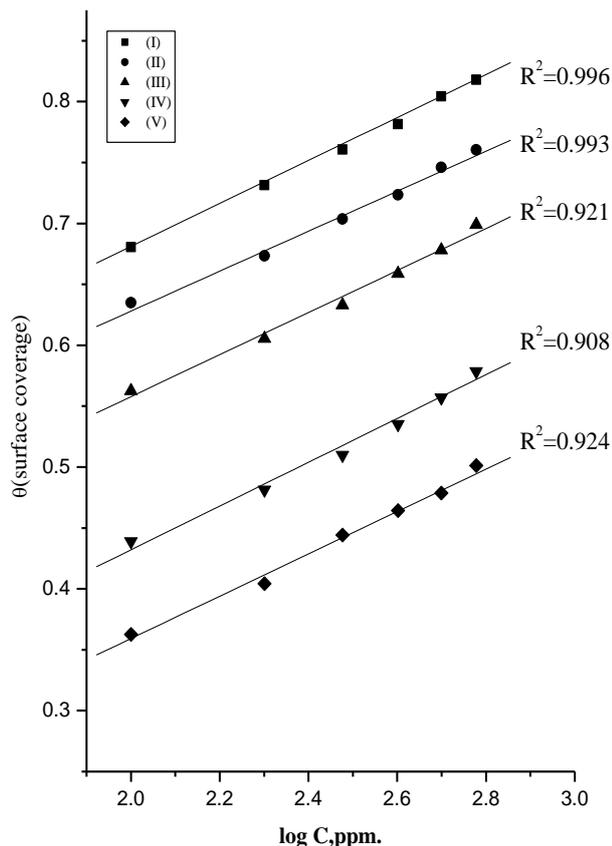


Figure 5 – Curve fitting of corrosion data for 316L SS HCl in presence of different concentrations of inhibitors to the Temkin isotherm at 30 °C

3.4. Effect of Temperature

The effect of temperature (30 – 55°C) on the performance of the inhibitors at a concentration of (1× 10⁻⁶ - 11× 10⁻⁶ M) for 316L SS in 3M HCl was studied using Weight-loss measurements. Plots of log k (corrosion rate) against 1/ T (absolute temperature) Figure 6 for 316L SS in 3M M HCl, gave straight lines. The values of the slopes obtained at different temperatures permit the calculation of Arrhenius activation energy (E_a^{*}). The activation energy values obtained from these lines were found to be 58 kJ mol⁻¹ for 316L SS 3M HCl and 3 kJ mol⁻¹ for acid containing inhibitors 3, Table 7.

Table 7 - Effect of concentrations of inhibitors on the activation energy of 316L SS dissolution in 3M HCl.

Concentration, M	Activation energy, E _a [*] , kJ mol ⁻¹				
	(I)	(II)	(III)	(IV)	(V)
0.0	58.0				
1×10 ⁻⁶	90.0	80.7	67.8	61.4	61.0
3×10 ⁻⁶	94.4	81.0	74.1	70.2	64.5
5×10 ⁻⁶	96.4	83.2	75.2	70.9	64.9
7×10 ⁻⁶	96.6	84.0	76.8	71.9	65.0
9×10 ⁻⁶	97.3	85.0	78.2	72.9	65.1
11×10 ⁻⁶	97.6	86.1	80.2	73.1	66.2

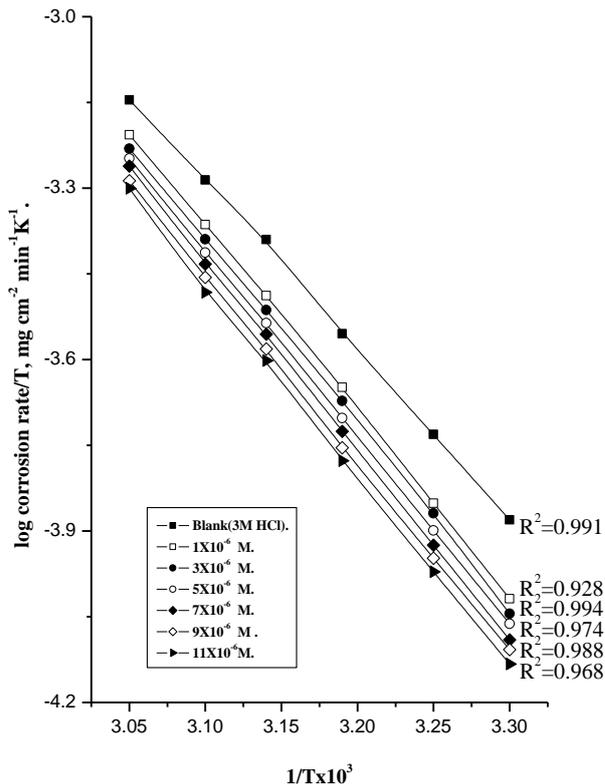


Figure 6 - log (corrosion rate/T) – (1/T) curves for 316L SS dissolution in 3M HCl in absence and presence of different concentrations of inhibitor (I)

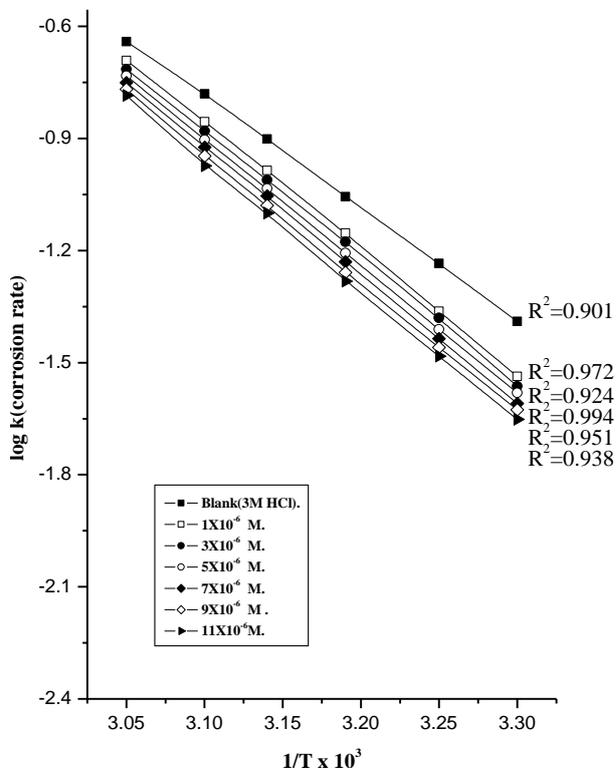


Figure 7 – log k – 1/T curves for 316L SS dissolution in 3M HCl in absence and presence of different concentrations of inhibitor (I)

Activation parameters for corrosion of zinc were calculated from Arrhenius – type plot.

$$k = A \exp(-E_a^*/RT) \quad (6)$$

and transition state- type equation :

$$k = RT / Nh \exp(\Delta S^*/R) \exp(-\Delta H^*/RT) \quad (7)$$

The relation between $\log k/T$ vs. $1/T$ gives straight line, from its slope, ΔH^* can be computed and from its intercept ΔS^* can be also computed Figure 7.

Tables 8 and 9 exhibits the values of apparent activation energy E_a^* , enthalpies ΔH^* and entropies ΔS^* for 316L SS in dissolution in 3M HCl solution. The presence of derivatives increases the activation energies of 316L SS indicating strong adsorption of the inhibitor molecules on the metal surface and the presence of these additives induces energy barrier for the corrosion reaction and this barrier increases with increasing the additive concentrations.

Table 8 - Effect of concentrations of inhibitors on the activation enthalpy of 316L SS dissolution in 3M HCl.

Concentration, M	Activation enthalpy, ΔH^* , kJ mol ⁻¹				
	(I)	(II)	(III)	(IV)	(V)
0.0	52.6				
1×10^{-6}	87.4	76.8	71.4	67.0	62.0
3×10^{-6}	89.5	78.7	71.9	67.1	62.2
5×10^{-6}	92.2	80.6	74.1	68.2	63.2
7×10^{-6}	92.6	81.3	75.5	69.2	63.3
9×10^{-6}	94.3	82.7	79.4	69.9	64.8
11×10^{-6}	94.3	83.4	80.2	70.2	65.1

Table 9 - Effect of concentrations of inhibitors on the activation entropy of 316L SS dissolution in 3M HCl.

Concentration, M	Activation entropy, $-\Delta S^*$, k ⁻¹ J mol ⁻¹				
	(I)	(II)	(III)	(IV)	(V)
0.0	82.8				
1×10^{-6}	7.3	25.0	41.0	54.5	70.0
3×10^{-6}	13.4	19.7	36.9	53.3	69.5
5×10^{-6}	20.9	14.4	33.5	51.6	69.0
7×10^{-6}	21.7	12.7	29.5	48.9	66.7
9×10^{-6}	26.0	8.8	17.4	47.3	66.0
11×10^{-6}	26.7	7.4	13.4	46.4	65.2

3.5. Electrochemical measurement

Galvanostatic polarization studies were carried out on 316LL SS in 3 M HCl solution without and with different concentrations of the inhibitors. The tested specimen was used as working electrode.

Saturated calomel electrode (SCE) was used as reference electrode while platinum wire as a counter electrode. All experiments were carried out at 30°C. The inhibition efficiency (%IE) is defined as [10]:

$$\%IE = ((i_{corr} - i_{inh.}) / i_{corr}) \times 100 \quad (8)$$

Where i_{corr} . and $i_{inh.}$ are the corrosion current density in the absence and presence of inhibitors respectively. The degree of surface area coverage (θ) can be calculated from the relation:

$$\theta = (i_{corr} - i_{inh.}) / i_{corr} \quad (9)$$

3.5.1. Polarization curves

Corrosion behavior of 316LL SS is studied in 3M HCl solutions in absence and presence of (1×10^{-6} – 11×10^{-6}) M inhibitors (I –V) at 30°C. Figure 7 show the galvanostatic polarization curve of 316LL SS in 3M HCl in absence and presence of inhibitor (I) at different inhibitor concentrations, Table (10) gives the various corrosion parameters.

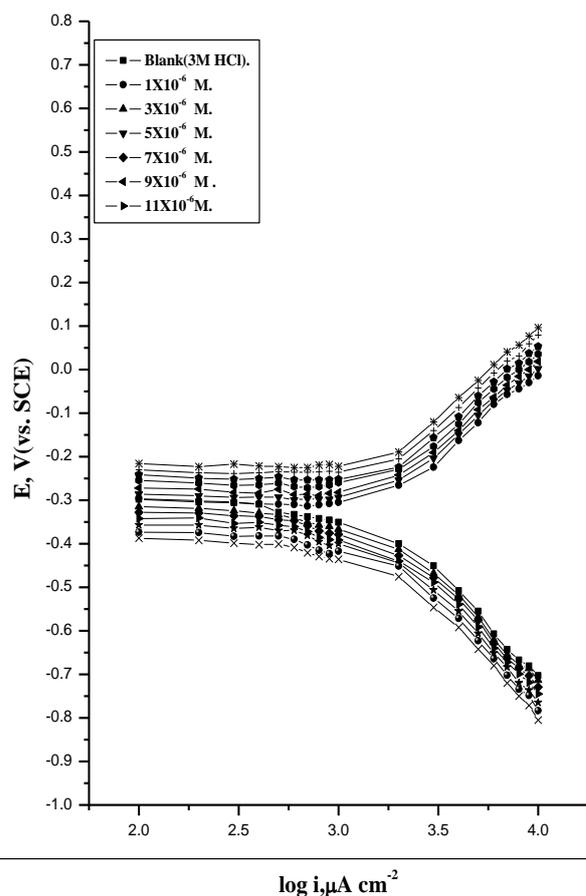


Figure 8 – Galvanostatic polarization curve of 316L SS in absence and presence of different concentration of inhibitor (I) at 30 °C

Tafel slopes (β_a & β_c) values, corrosion potential (E_{corr}), corrosion current (i_{corr}), degree of surface

coverage (θ) and inhibition efficiency (% IE) indicate that:

1- The corrosion current density decreases with increasing the concentration of organic derivatives derivatives. This indicates that the presence of these derivatives retards the dissolution of 316LL SS in 3M HCl solution and the degree of inhibition depends on the concentration and type of the inhibitor present as shown in Figure 8.

2 - The degree of surface coverage was found to increase with increasing the concentration of inhibitor.

3 - The presence of the tested inhibitors retards both anodic and cathodic reactions and hence these inhibitors act as mixed type inhibitors.

4 - The order of decrease in inhibition efficiency for the tested additives is:

Series 1: (I) > (II) > (III)

Series 2: (IV) > (V)

Table 10 - corrosion parameters for 316L ss in 3M HCl in absence and presence of different concentrations of inhibitors (I–V) at 30°C

Inhibitor	Conc., M	$-E_{cor}$, V	i_{cor} , μAcm^{-2}	B_a , mVdec ⁻¹	B_c , mVdec ⁻¹	θ	%IE
Blank	3M HCl	0.351	74.64	0.287	0.179	–	–
I	1×10^{-6}	0.317	54.81	0.109	0.462	0.3862	38.62
	3×10^{-6}	0.313	21.88	0.103	0.403	0.6143	61.43
	5×10^{-6}	0.303	20.79	0.162	0.351	0.7443	74.43
	7×10^{-6}	0.301	11.48	0.153	0.362	0.8462	84.62
	9×10^{-6}	0.297	11.21	0.148	0.298	0.8498	84.98
	11×10^{-6}	0.287	10.93	0.158	0.197	0.8535	85.35
II	1×10^{-6}	0.330	50.70	0.052	0.192	0.3208	32.08
	3×10^{-6}	0.319	32.81	0.056	0.243	0.5605	56.06
	5×10^{-6}	0.315	17.10	0.088	0.218	0.7709	77.09
	7×10^{-6}	0.306	13.68	0.113	0.207	0.8169	81.69
	9×10^{-6}	0.301	12.91	0.111	0.312	0.8270	82.70
	11×10^{-6}	0.297	11.56	0.103	0.301	0.8451	84.51
III	1×10^{-6}	0.333	51.40	0.051	0.190	0.2940	29.40
	3×10^{-6}	0.331	36.30	0.061	0.208	0.5355	53.55
	5×10^{-6}	0.327	28.18	0.083	0.206	0.6656	66.56
	7×10^{-6}	0.316L	14.36	0.069	0.347	0.7672	76.72
	9×10^{-6}	0.312	15.83	0.110	0.351	0.7879	78.79
	11×10^{-6}	0.297	14.96	0.097	0.309	0.7995	79.95
IV	1×10^{-6}	0.339	57.81	0.063	0.425	0.2255	22.55
	3×10^{-6}	0.333	36.31	0.077	0.392	0.4962	49.62
	5×10^{-6}	0.326	29.38	0.084	0.391	0.6295	62.95
	7×10^{-6}	0.323	18.71	0.114	0.386	0.7407	74.07
	9×10^{-6}	0.316L	17.96	0.127	0.389	0.7593	75.93
	11×10^{-6}	0.302	15.32	0.132	0.371	0.7947	79.47
V	1×10^{-6}	0.341	59.71	0.064	0.427	0.2000	20
	3×10^{-6}	0.336	40.38	0.089	0.393	0.4590	45.90
	5×10^{-6}	0.325	30.42	0.093	0.390	0.5924	59.24
	7×10^{-6}	0.321	21.21	0.128	0.372	0.7158	71.58
	9×10^{-6}	0.302	18.51	0.136	0.363	0.7520	75.20
	11×10^{-6}	0.292	16.21	0.148	0.348	0.7828	78.28

The inhibition mechanism of the tested inhibitor is a combination of surface blockage and electrostatic repulsion between adsorbed surfactant layer and chloride ions. The adsorption density of inhibitor depends on the inhibitor concentration. At ad-

sorption density less than that needed for monolayer coverage Figure 9a, most of the nucleation sites are still possibly exposed to HCl, as the inhibitor has less adsorption affinity on them. When the adsorption density reaches monolayer adsorption

Figure 9b, some of the nucleation sites begin to be completely covered by inhibitor molecules. At maximum adsorption density in Figure 9c, the whole

surface, including the nucleation sites, is covered by the inhibitor molecules and hence complete inhibition occurs.

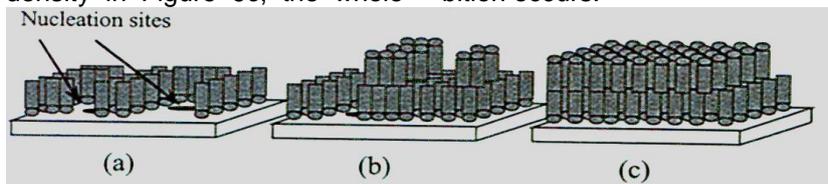


Figure 9 - Adsorption schemes for organic compound as an inhibitor on 316L SS stainless steel, (8a) at low concentrations, (8b) intermediate concentrations and (8c) high concentrations

3.5.2 Effect of applied cyclic stresses on the corrosion behavior of stainless steel 304 SS

In these experiments the measurements were carried out in 3 M HCl solution at 30°C in absence and presence of different inhibitors at different concentrations (5×10^{-6} M – 11×10^{-6} M), while applying cyclic stresses (82Mpa - 247Mpa) with number of cycles (63000) at 10.5 Hz. The galvanostatic polarization curves were plotted for each inhibitor. In the rotating cantilever bending fatigue test, the tension and compression cyclic stresses occur at the outer surfaces of the specimen, for this reason plastic deformation commonly occurs by the slip of one plane over the other. Such slip is very non-uniform within a polycrystalline solid and can occur on only some of the crystal planes within a metal grain [11]. Stressed 316L SS surfaces by the rotating cantilever bending fatigue test, contain iron atoms that are more reactive hence they have a less stable crystalline environment and more susceptible to attack. Whenever a metal is stressed, the metallic crystal lattice becomes severely strained and tends to become more anodic, hence they travel into solution more readily than the atoms in less strained sites. Consequently, corro-

sion of the most strained regions of a metal have the highest rate of corrosion.

The polarization curves were plotted for each inhibitor as shown in Figure 10. The results indicate that, the inhibition efficiency of inhibitors (I –V) for the corrosion of 316L SS in the acidic solution at 30°C is decreased in order Series 1: (I) > (II) > (III) and Series 2: (IV) > (V) with increasing the concentration of inhibitors and decreased with increasing applied cyclic stresses as shown in Table 11. The corrosion of the most strained regions of the tested specimens is most rapid, also the adsorbed layer of inhibitor on stainless steel surface becomes less stable and the corrosive media becomes more aggressive. Inspection of Tafel slopes values and E_{corr} values under these conditions indicate that these inhibitors act as mixed – type inhibitors. Also, the corrosion current density i_{corr} increased with increasing the applied cyclic stresses. The increase in the applied cyclic stress adds to the free energy of the strained atoms and hence more atoms go to the solution causing a pronounced increase in the corrosion current density.

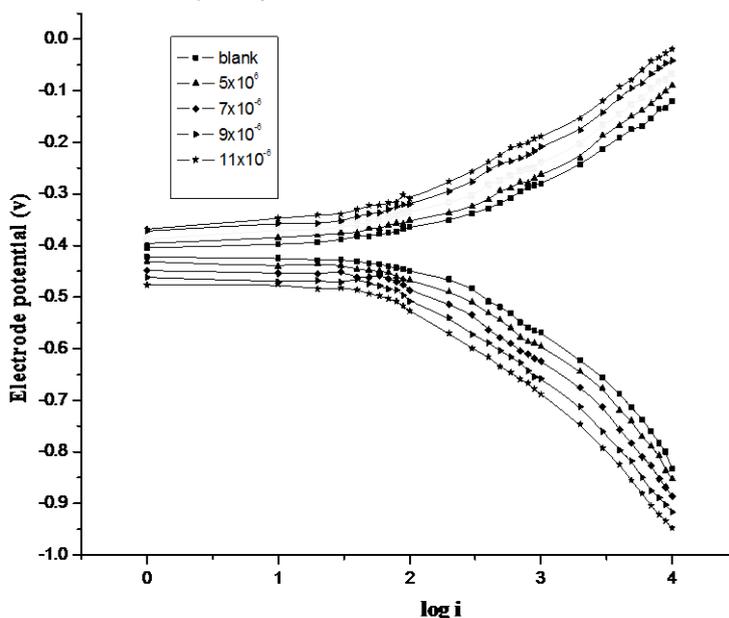


Figure 10 – Galvanostatic polarization curves of 316L SS in 3M HCl in absence and presence of inhibitor (I) at various concentrations at 30 °C

Table 11 - Corrosion parameters for 316L SS in 3M HCl in absence and presence of different concentrations of inhibitors (I–V) for stressed specimen by 247 MPa, at 63000 cycles at 30°C

Inhibitor	Conc., M	-E _{cor} , V	i _{corr} , μAcm ⁻²	B _a , mVdec ⁻¹	B _c , mVdec ⁻¹	θ	%IE
Blank	2M HCl	0.391	141.25	0.280	0.325	–	–
I	5×10 ⁻⁶	0.382	107.15	0.197	0.352	0.2414	24.14
	7×10 ⁻⁶	0.381	102.80	0.211	0.399	0.2722	27.22
	9×10 ⁻⁶	0.376	79.72	0.161	0.347	0.3081	30.81
	11×10 ⁻⁶	0.372	93.32	0.173	0.325	0.3393	33.93
II	5×10 ⁻⁶	0.381	109.64	0.140	0.338	0.2237	22.37
	7×10 ⁻⁶	0.380	107.15	0.162	0.325	0.2414	24.14
	9×10 ⁻⁶	0.379	105.19	0.137	0.317	0.2552	25.52
	11×10 ⁻⁶	0.374	102.32	0.158	0.330	0.2586	25.86
III	5×10 ⁻⁶	0.369	118.85	0.279	0.431	0.1586	15.86
	7×10 ⁻⁶	0.367	117.76	0.293	0.407	0.1663	16.63
	9×10 ⁻⁶	0.361	106.69	0.272	0.398	0.2446	24.46
	11×10 ⁻⁶	0.349	106.32	0.235	0.379	0.2472	14.72
IV	5×10 ⁻⁶	0.366	128.23	0.307	0.396	0.92	9.2
	7×10 ⁻⁶	0.355	125.89	0.310	0.413	0.1087	10.87
	9×10 ⁻⁶	0.360	110.42	0.417	0.462	0.2182	21.82
	11×10 ⁻⁶	0.362	108.65	0.299	0.397	0.2307	23.07
V	5×10 ⁻⁶	0.361	131.25	0.306	0.382	0.0707	7.07
	7×10 ⁻⁶	0.357	128.74	0.312	0.405	0.0885	8.85
	9×10 ⁻⁶	0.361	123.66	0.423	0.446	0.1245	12.45
	11×10 ⁻⁶	0.364	122.64	0.405	0.376	0.1317	13.17

4. CONCLUSIONS

The following conclusions can be deduced from the present study:

1- Derivatives appear to be efficient inhibitors for corrosion of 316L in 3MHCl solution, which act as mixed type inhibitors, the %IE was found to increase by increasing the inhibitor concentration and was found inhibitor (I) with high molecular weight which gives the highest inhibition efficiency over the other derivatives Series 1: (I) > (II) > (III) and Series 2: (IV) > (V).

2 - The inhibition of corrosion of 316LL SS in 3M HCl solution was found to obey the Temkin adsorption isotherm and the inhibitors appear to add to the passive layer formed on the tested 316L SS.

3 - Derivatives can be used as inhibitors to fatigue corrosion of 316L SS in HCl solution and these materials act as a mixed type inhibitors.

4 -The inhibition efficiency (%IE) increases with the increase in the inhibitor concentration, while decreases with the increase in the cyclic stress and the order of intensity of inhibition efficiency of

inhibitors used was Series 1: (I) > (II) > (III) and Series 2: (IV) > (V).

5 -The corrosion current density increases with the increase in the cyclic stresses.

REFERENCES

- [1] L. Niu, C.N. Cao, H.C. Lin, G.L. Song (1998), "Inhibitive effect of benzotriazole on the stress corrosion cracking of 18cr-9ni-ti stainless steel in acidic chloride solution" *Corros. Sci.*, no 40(7), pp. 1109-1117.
- [2] D.E.Davies, J.P.Dennison, A.A.Odeh (1985), Proceedings of 6th European Symposium on Corrosion Inhibitors (6th. SEIC), ANN. Univ. Ferrara, N.S. Sez. V. Suppl. no. 8, pp. 669.
- [3] A.Frignani, G.Trabanelli, F.Zucchi (1984), "the use of slow strain rate technique for studying stress corrosion cracking inhibition" *Corros. Sci.*, no24, pp.917-927
- [4] F.Zucchi, G.Trabanelli, A. Frignani, V.Carassiti, (1973), *5eme Congress European de Corrosion*, Paris, 24-28 September, pp. 217.
- [5] X. Z.Chen, S.H. Wu (1985), Proceedings of the 6th European Symposium on Corrosion Inhibitors (6th. SEIC), ANN. Univ. Ferrara, N.S. Sez. V. Suppl. no. 8, pp 677.

- [6] C.N.Cao, , Q.G.Yang, , M.Lu, H.C.Lin (1992), "you liang de nai shi cai liao hua gang yan zhe jiang sheng dong tou xian hua gang yan kai cai zong chang cai fang ce ji" *J. Chinese Soc. Corros. Protection*, no.2, pp.109-115
- [7] C. N. Cao, *Corrosion Science and protection Technique* (1990), no.2, pp. 1
- [8] G.Schmilt, K.Bedbur (1985) "Investigations on structural and electronic effects in acid inhibitors by AC impedance", *Werkst. Ú.Korros*, no. 36, pp. 273-278
- [9] E. Khamis, E.S.H. El- Ashry, A.K. Ibrahim (2000)," Synergistic action of vinyl triphenyl phosphonium bromide with various anions on corrosion of steel" *Br. Corros.J.*, no35 (2), pp.150-154
- [10] Y.A.El- Awady, A.I. Ahmed (1985)," Effect of temperature and inhibitors on the corrosion of aluminum in 2N HCl solution, A kinetic study" *J. Ind. Chen.*, no.24 , pp.601-617
- [11] E. Dieter George, *Mechanical Metallurgy*, University of Maryland, (1988).

IZVOD

UTICAJ INHIBITORA DERIVATA AZINA I DIAZINA NA KOROZIJU NERĐAJUĆEG ČELIKA 316 LSS U KISELOJ SREDINI

Inhibitorski efekat nekih derivata azina i diazina na koroziju 316L SS uzoraka u 3 M HCl u prisustvu organskih derivata sa koncentracijama ($1 \times 10^{-6} M - 11 \times 10^{-6} M$) na 30°C je ispitivan preko gubitka težine i tehnikom galvanske polarizacije. Inhibitorski efekat ovih derivata na ravnomernost korozije uzoraka je ocenjivan preko anodnih i katodnih polarizacionih krivih elektrode u testiranim medijima. Ispitivani derivati vršili su inhibiciju korozije ispitivanih uzoraka. Polarizaciona ispitivanja su pokazala da se ovi derivati ponašaju kao mešani inhibitori i inhibiraju koroziju adsorpcijom čestica inhibitora na površini uzorka zbog prisustva više od jednog aktivnog centar u molekulima inhibitora. Adsorpcija se ponaša prema Temkinovoj adsorpcionoj izotermi. Dodavanjem I⁻, BR⁻ i SCN⁻ jona u rastvor koji sadrži organske derivate povećava se efikasnost inhibicije sistema.

Ključne reči: organski derivati; Inhibicija; ciklični stres; kiselina sredina; nerđajući čelik 316L SS

Originalni naučni rad

Primljeno za publikovanje: 17. 07. 2014.

Prihvaćeno za publikovanje: 14. 09. 2014.